



# Report EN13773

Document number:	202301856	Report date:	9/06/2023
Fabric reference:	Jermian		
	01- Metal (BPZ-008602)	Date analyses:	9/06/2023
Customer:	Verotex Industries	Place analyses:	Labotex
	Edisonweg 3	Date of request:	7/06/2023
	5466 AR Veghel	Samples received:	7/06/2023
	Netherlands		

Testing and conditioning in standard atmosphere, T (20±2)°C and RH (65±4)%

Specification	Results	Remarks	I
---------------	---------	---------	---


## Burning behaviour of fabrics for curtains drapes

EN13773

conditioning min 24h in  
standard atmosphere

used gas: propane  
flame height: 40mm  
bottom edge ignition:  
size EN1101: 200x80mm  
size EN13772: 560x170mm

flowchart EN13773

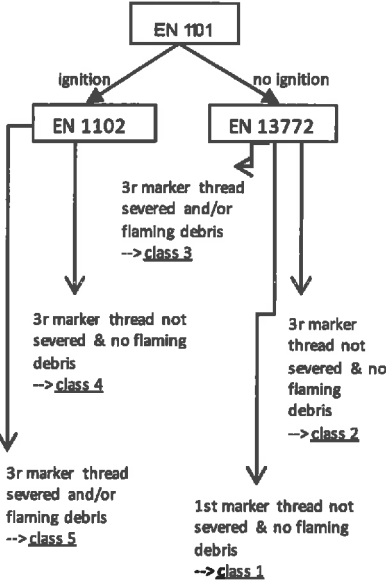

## EN 1101

Test EN1101 is performed after subjecting the fabric to 1 washing cycle,

based on the recommended washing instructions.

flame application time	warp	weft
1s	no ignition	no ignition
2s	no ignition	no ignition
3s	no ignition	no ignition
4s	no ignition	no ignition
5s	no ignition	no ignition
10s	no ignition	no ignition
15s	no ignition	no ignition
20s	no ignition	no ignition

Mean ignition time warp:	0.0
Mean ignition time weft:	0.0
Minimum ignition time:	0.0



Report EN13773

Document number:	202301856	Report date:	9/06/2023
Fabric reference:	Jermian		
	01- Metal (BPZ-008602)	Date analyses:	9/06/2023
Customer:	Verotex Industries	Place analyses:	Labotex
	Edisonweg 3	Date of request:	7/06/2023
	5466 AR Veghel	Samples received:	7/06/2023
	Netherlands		

Testing and conditioning in standard atmosphere, T (20±2)°C and RH (65±4)%

Specification	Results				Remarks	!
<u>EN13772 after washing</u>						
warp	face	reverse	reverse	reverse		
1st marker thread severed	no	no	no	no		
2nd marker thread severed	no	no	no	no		
3rd marker thread severed	no	no	no	no		
time to severance 3rd marker thread (s)	0	0	0	0		
destroyed length (mm)	166	143	133	135		
flaming debris	no	no	no	no		
weft	face	reverse	face	face		
1st marker thread severed	no	no	no	no		
2nd marker thread severed	no	no	no	no		
3rd marker thread severed	no	no	no	no		
time to severance 3rd marker thread (s)	0	0	0	0		
destroyed length (mm)	130	147	152	161		
flaming debris	no	no	no	no		
<u>EN13772 before washing</u>						
warp	face	reverse	reverse	reverse		
1st marker thread severed	no	no	no	no		
2nd marker thread severed	no	no	no	no		
3rd marker thread severed	no	no	no	no		
time to severance 3rd marker thread (s)	0	0	0	0		
destroyed length (mm)	156	135	151	140		
flaming debris	no	no	no	no		
weft	face	reverse	face	face		
1st marker thread severed	no	no	no	no		
2nd marker thread severed	no	no	no	no		
3rd marker thread severed	no	no	no	no		
time to severance 3rd marker thread (s)	0	0	0	0		
destroyed length (mm)	160	119	136	129		
flaming debris	no	no	no	no		



Report EN13773

Document number:	202301856	Report date:	9/06/2023
Fabric reference:	Jermian		
	01- Metal (BPZ-008602)	Date analyses:	9/06/2023
Customer:	Verotex Industries	Place analyses:	Labotex
	Edisonweg 3	Date of request:	7/06/2023
	5466 AR Veghel	Samples received:	7/06/2023
	Netherlands		

Testing and conditioning in standard atmosphere, T (20±2)\*C and RH (65±4)%

Specification	Results	Remarks	!
Classification			
Class 1	X		
Class 2			
Class 3			
Class 4 or 5			



Labotex certifies that the results mentioned in this report are obtained after testing in accordance with the procedure and equipment specified by the concerned standards, unless noted differently.

Annick Gijsemans - Laboratory Manager

Labotex has the competence to perform tests in accordance with the requirements of standard NBN EN ISO/IEC 17025. The scope of this accreditation can be consulted on the BELAC website [https://mg3.economie.fgov.be/NL/belac/labotesting/applic/accreditedc\\_nl.asp?certificatienummer=364-TEST](https://mg3.economie.fgov.be/NL/belac/labotesting/applic/accreditedc_nl.asp?certificatienummer=364-TEST)  
Sampling is performed by the costumer. Fabric analysed as recieved. The results in this report only relate to the tested items.  
Samples will be returned to the customer together with the certificate, if possible. Samples will not be retained, unless specified by the customer. Retained samples will be kept for maximum one year unless a specific retention period is necessary.  
This report cannot be copied unless in its complete form and with written approval of Labotex (Kontich).  
Uncertainty of measurement on the test result is not taken into account when assessing compliance with the specifications. When results are compliant to the specification, the square next to the result is empty. When the result is not compliant to the specification, the square is filled with a flag "V".  
The uncertainty and the description of the methods are available at the lab on request.