

Document number: 202201668
 Fabric reference: XFR-Jabberwocky
 Customer: Verotex Industries BV
 Edisonweg 3
 5466 AR Veghel
 Netherlands

Report date: 1/07/2022
 Date analyses: 1/07/2022
 Place analyses: Labotex
 Date of request: 8/06/2022
 Samples received: 9/06/2022

Testing and conditioning in standard atmosphere, T (20±2)°C and RH (65±4)%

Specification	Results	Remarks
---------------	---------	---------

Burning behaviour of fabrics for curtains drapes

EN 1101


Test EN1101 is performed after subjecting the fabric to 1 washing cycle, based on the recommended washing instructions.

EN13773

conditioning min 24h in standard atmosphere

used gas: propane
 flame height: 40mm
 bottom edge ignition:
 size EN1101: 200x80mm
 size EN13772: 560x170mm

flowchart EN13773

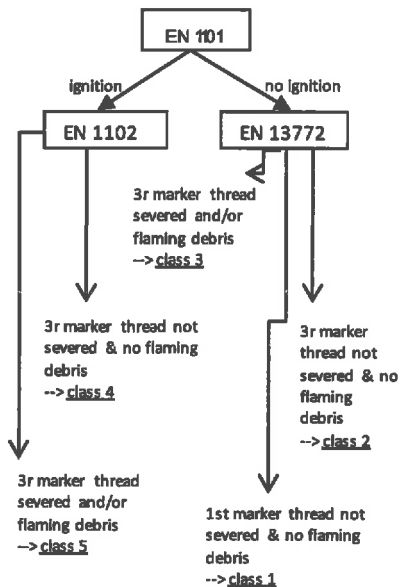

flame application time	warp	weft
1s	no ignition	no ignition
2s	no ignition	no ignition
3s	no ignition	no ignition
4s	no ignition	no ignition
5s	no ignition	no ignition
10s	no ignition	no ignition
15s	no ignition	no ignition
20s	no ignition	no ignition

Mean ignition time warp: 0.0
 Mean ignition time weft: 0.0
 Minimum ignition time: 0.0



Report EN13773

Document number:	202201668	Report date:	1/07/2022
Fabric reference:	XFR-Jabberwocky	Date analyses:	1/07/2022
Customer:	Verotex Industries BV Edisonweg 3 5466 AR Veghel Netherlands	Place analyses:	Labotex
		Date of request:	8/06/2022
		Samples received:	9/06/2022

Testing and conditioning in standard atmosphere, T (20±2)°C and RH (65±4)%

Specification	Results				Remarks
EN13772 after washing					
warp	face	reverse	reverse	reverse	
1st marker thread severed	no	no	no	no	
2nd marker thread severed	no	no	no	no	
3rd marker thread severed	no	no	no	no	
time to severance 3rd marker thread (s)	0	0	0	0	
destroyed length (mm)	149	159	152	142	
flaming debris	no	no	no	no	
weft	face	reverse	face	face	
1st marker thread severed	no	no	no	no	
2nd marker thread severed	no	no	no	no	
3rd marker thread severed	no	no	no	no	
time to severance 3rd marker thread (s)	0	0	0	0	
destroyed length (mm)	145	142	135	146	
flaming debris	no	no	no	no	
EN13772 before washing					
warp	face	reverse	reverse	reverse	
1st marker thread severed	no	no	no	no	
2nd marker thread severed	no	no	no	no	
3rd marker thread severed	no	no	no	no	
time to severance 3rd marker thread (s)	0	0	0	0	
destroyed length (mm)	168	164	166	194	
flaming debris	no	no	no	no	
weft	face	reverse	face	face	
1st marker thread severed	no	no	no	no	
2nd marker thread severed	no	no	no	no	
3rd marker thread severed	no	no	no	no	
time to severance 3rd marker thread (s)	0	0	0	0	
destroyed length (mm)	136	152	147	160	
flaming debris	no	no	no	no	



Report EN13773

Document number:	202201668	Report date:	1/07/2022
Fabric reference:	XFR-Jabberwocky		
Customer:	Verotex Industries BV Edisonweg 3 5466 AR Veghel Netherlands	Date analyses:	1/07/2022
		Place analyses:	Labotex
		Date of request:	8/06/2022
		Samples received:	9/06/2022

Testing and conditioning in standard atmosphere, T (20±2)°C and RH (65±4)%

Specification	Results	Remarks
Classification		
Class 1	X	
Class 2	-----	
Class 3	-----	
Class 4 or 5	-----	



Labotex certifies that the results mentioned in this report are obtained after testing in accordance with the procedure and equipment specified by the concerned standards, unless noted differently.

Annick Gijsemans - Laboratory Manager

Labotex has the competence to perform tests in accordance with the requirements of standard NBN EN ISO/IEC 17025. The scope of this accreditation can be consulted on the BELAC website https://ng3.economie.fgov.be/nl/belac/labotesting/applic/accredited_nl.asp?certificatienummer=364-TEST

Sampling is performed by the customer. Fabric analysed as recieved. The results in this report only relate to the tested items. Samples will be returned to the customer together with the certificate, if possible. Samples will not be retained, unless specified by the customer. Retained samples will be kept for maximum one year unless a specific retention period is necessary.

This report cannot be copied unless in its complete form and with written approval of Labotex (Kontich).

Uncertainty of measurement on the test result is not taken into account when assessing compliance with the specifications. When results are compliant to the specification, the square next to the result is empty. When the result is not compliant to the specification, the square is filled with a flag "V".

The uncertainty and the description of the methods are available at the lab on request.